

Use of Unconventional Aggregates in Hot Mix Asphalt Concrete

Viktors Haritonovs

Dept. of Roads and Bridges, Riga Technical University, Riga, Latvia

Abstract: The study investigates use of dolomite sand waste as filler or/and sand material plus BOF steel slag as fine and coarse aggregate for design of high performance asphalt concrete. Both environmental and economic factors contribute to the growing need for the use of these materials in asphalt concrete pavements. This is particularly important for Latvia, where local crushed dolomite and sandstone does not fulfill the requirements for mineral aggregate in high and medium intensity asphalt pavements roads. Annually 100 to 200 thousand tons of steel slag aggregates are produced in Latvia. However, it has not been used extensively in asphalt pavement despite its high performance characteristics. Dolomite sand waste, which is byproduct of crushed dolomite production, is another widely available polydisperse by-product in Latvia. Its quantity has reached a million of tons and is rapidly increasing. This huge quantity of technological waste needs to be recycled with maximum efficiency. Various combinations of steel slag, dolomite sand waste and conventional aggregates were used to develop AC 11 asphalt concrete mixtures. The mix properties tests include resistance to permanent deformations (wheel tracking test, dynamic creep test) and fatigue resistance. Laboratory test results showed that asphalt concrete mixtures containing steel slag and local limestone in coarse portion and dolomite sand waste in sand and filler portions had high resistance to plastic deformations and good resistance to fatigue failure.

Key words: Steel slag, dolomite sand waste, permanent deformation, creep test, fatigue.

1. Introduction

Asphalt concrete pavements are constructed of bituminous and polydisperse granular materials. Regardless of the thickness or type of asphalt pavement, the load is transmitted through the aggregate, the bitumen serving as a cementing agent to bind the aggregate in proper position to transmit the applied wheel loads to underlying layers where the load is finally dissipated [1, 2].

Local crushed dolomite and sandstone aggregate lack the desirable qualities for asphalt concrete mix design [3]. In the meantime, as natural supplies of high quality granular materials used in highways have become less abundant, the highway engineer is faced with the challenge of finding alternative materials to meet the requirements for these materials [4]. Some of these alternatives are fly ash, coal dust, hydrated lime, steel slag etc. [5]. The co-products (slag) of iron

and steel production have been used commercially since 19th century [6]. In the EU and North America steel slag is used in: bituminous bound materials; pipe bedding; hydraulically bound mixtures for subbase and base; unbound mixtures for subbase; capping; embankments and fill construction; clinker manufacture and fertilizer and soil improvement agent [7, 8]. However, in Latvia, for commercial road construction purposes, it has been used only for unbound mixtures.

The research has showed that production of asphalt mixtures with high performance characteristics is possible by using steel slag aggregate [9]. However, the studies have also indicated that, because of the high angularity and texture of the particles, the asphalt often has poor workability [10]. Therefore, the application of slag may have more potential in combination with conventional aggregates [11].

The second most widespread co-product in Latvia is the dolomite waste sand. It has been accumulating in quarries for many years and currently its quantity has reached several million tones. Previously it has been used in agriculture as the lime substitute for soil treatment and in the building industry as the quartz sand equivalent. Currently researchers in Latvia also offer to utilize the dolomite sand waste in the concrete production [12]. However, the research on the perspective use of dolomite waste sand in production of asphalt has received relatively little attention. For example, this material could be used to fully or partially replace the fine and filler portions.

The goal of this study is to develop high performance properties asphalt mixtures using various combinations of BOF steel slag, dolomite sand waste, crushed quartz sand and crushed dolomite aggregates and to compare the results with reference asphalt mixture, produced with conventional aggregates. The mix properties tests include resistance to permanent deformations (wheel tracking test, dynamic creep test) and fatigue resistance.

2. Materials

The basic materials used in this study are fractionated steel slag, crushed dolomite aggregate; dolomite sand waste, crushed quartz sand, unmodified bitumen B70/100 and SBS modified bitumen PMB 45/80-55. Steel slag was obtained from JSC Liepajas metalurgs (Latvia), dolomite sand waste from Plavinu DM Ltd (Latvia), crushed quartz sand from Jauncerpji Ltd. (Latvia) and crushed dolomite aggregate from AB Dolomitas (Lithuania), 70-100 penetration bitumen from PC Orlen (Lithuania) and SBS modified bitumen from Grupa LOTOS S.A (Poland). Conventional aggregate and unmodified and modified bitumen are used extensively for local mixes.

2.1 Properties of Dolomite Sand Waste

The Latvian law classifies steel slag and dolomite sand waste as non-hazardous solid materials (91/689 EEK). Chemical analysis of dolomite sand is shown in

Table 1. There is no evidence of clay minerals being present in dolomite sand. The X-ray diffraction has been used to obtain mineralogical composition of the investigated dolomite waste [12]. The main constituents of waste dolomite are $\text{CaCO}_3 \cdot \text{MgCO}_3$, which accounts for more than 92% of the composition.

This material contains more than 10% of fines (below 0.063 mm) and therefore it has to be tested for properties of mineral filler (Fig. 1). The fine particles of this material are part of the mixture mineral carcass and contribute to obtaining a dense structure by filling the voids between coarse aggregate particles. The mineral filler that is in this material, however, provides more touch points between fine and coarse aggregate thus improving the mechanical properties of the mixture. Another function of the mineral filler is to increase the bitumen viscosity and improve the properties of binder.

Table 2 contains test results of conventional sand and dolomite filler for comparison of the properties of sand waste's fine portion and filler portion respectively. The properties of the both of these fractions correspond to high quality requirements. Dolomite waste sand test results present excellent angularity with average flow coefficient of 33. Test results show that the fines quality is high—the material has low MB (methylene blue)

Table 1 Chemical properties of dolomite sand waste.

Oxide	CaO	MgO	SiO ₂	Na ₂ O	Al ₂ O ₃	K ₂ O	Fe ₂ O ₃
%	31.0	17.0	2.5	0.82	0.64	0.76	0.34

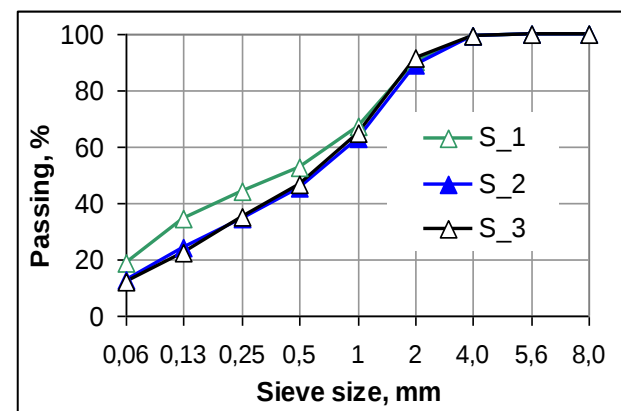


Fig. 1 Particle size distribution of dolomite sand.

Table 2 Physical and mechanical characteristics of dolomite sand.

Physical and mechanical properties	Unit	Related standard	Value		
			Dolomite waste sand	Conventional material	
				Crushed quartz sand	Dolomite filler
Sand equivalent test	%	LVS EN 933-8	60	91	-
Flow coefficient	sec	LVS EN 933-6	33	35	-
Water absorption	%	LVS EN 1097-6	2.0	5.4	< 2.6
Grain density	mg/m ³	LVS EN 1097-6	2.80	2.80	2.75
Fine content	%	LVS EN 933-1	12-19	0.9	78-88
Methylene blue test	g/kg	LVS EN 933-9	0.5	-	0.5
Carbonate content	%	LVS EN 196-21	> 90	-	> 90
Rigden air voids	%	LVS EN 1097-4	28-38	-	28-38
Delta ring and ball test	°C	LVS EN 13179-1	8-25	-	8-25

Table 3 Physical and mechanical characteristics of steel slag aggregate.

Physical and mechanical properties	Unit	Related standard	Value	
			Steel slag aggregate	Crushed dolomite aggregate
LA (Los Angeles) coefficient	%	LVS EN 1097-2	19	22
Resistance to wear. Nordic test (A _N)	%	LVS EN 1097-9	14.4	15.7
FI (flakiness index)	%	LVS EN 933-3	2	12
Water absorption	%	LVS EN 1097-6	2.4	2.7
Grain density	Mg/m ³	LVS EN 1097-6	3.25	2.80
Fine content	%	LVS EN 933-1	0.5	0.9
Freeze/thawing (MS)	%	LVS EN 1367-2	3	9
Expansion	%	LVS EN 1744-1	2	-

value—0.5 high carbonate content—more than 90%, excellent Rigden air voids and Delta ring and ball tests results

2.2 Properties of Steel Slag Aggregate

The properties of BOF steel slag correspond to the highest category of LVE EN 13043 standard. However, because of high abrasivity of this material, the proportion of it for wearing courses according to Latvian Road Specifications 2012 has been restricted to 20 present. The test results of steel slag main properties show very low FI—2, excellent mechanical strength with average LA value of 19, high frost resistance with average MS value of 3, low fines content—0.5% and slag expansion tests, showed that the expected swelling should be negligible (Table 3).

2.3 Bitumen Tests

Unmodified bitumen BND 60/90 (category defined in accordance to Russian specifications) and SBS

polymer modified bitumens was used for the testing. All the test results of the bitumen BND 60/90 and PMB are shown in Table 4.

3. Mix Design

Dense graded AC mixtures have been designed by using conventional and unconventional raw materials. The Marshall mix design procedure was used for the determination of the optimal bitumen content for the reference mixture, considering the mixture test results for Marshall stability and flow, as well as the volumetric values: V (air voids), VMA (voids in mineral aggregate) and VFB (voids filled with bitumen) [13]. Test specimens for Marshall Test were prepared in the laboratory by impact compactor according to LVS EN 12697-30 with 2×50 blows of hammer 140 °C temperature. The optimal bitumen content was determined by optimisation of the volumetric characteristics. Variation of bitumen content even with having similar grading curves can result in high hygroscopicity of dolomite waste material,

Table 4 Typical characteristics of the bitumens.

Parameter	Bitumen				Standard
	BND 60/90	PMB 10/40-65	PMB 45/80-55	PMB 25/55-60	
Penetration at 25 °C, dmm	65.0	40.0	50.0	34.0	LVS EN 1426
Softening point, °C	50.4	65	58.4	63.5	LVS EN 1427
Fraas temperature, °C	-25	-17	-20	-23	LVS EN 12593
Kinematic viscosity, mm ² /s	607	2,390	1,203	1,712	LVS EN 12595
Dynamic viscosity, Pa s	340	4,166	1,074	3,021	LVS EN 12596
Elastic recovery, %	-	87	88	89	LVS EN 13398
Ageing characteristics of bitumen under the influence of heat and air (RTFOT method)					
Loss in mass, %	0.1	0.01	0.02	0.02	LVS EN 12607-1
Retained penetration, %	70.8	75	69.7	79.4	LVS EN 1426
Increase of a softening point, °C	6.4	7.2	5.9	6.2	LVS EN 1427
Fraas breaking point after aging, °C	-20.0	-15	-18	-19	LVS EN 12593

differences in aggregate bulk density and high bitumen absorption of BOF steel slag material [14, 15].

4. Performance Evaluation

Three different groups of mixtures were analyzed:

- Two reference mixtures without co-products (with conventional and SBS bitumen), which were used as a control;
- Mixtures containing only BOF slag and dolomite waste sand;
- Combination of conventional and unconventional materials.

Performance tests are time-consuming and the number of combinations is very large; therefore in the first phase the different mixtures were evaluated with axial and triaxial loads. The combinations that have the highest deformation resistance will be tested for rut resistance and fatigue (see Fig. 2).

4.1 Uniaxial and Triaxial Test

For this test the standard LVS EN 12697-25 was followed. The uniaxial and triaxial cyclic compression test is performed using specimens with 101.7 mm diameter and 63.5 ± 2.5 mm height. The laboratory specimens were compacted using Marshall Impact compactor. The applied load had a block-pulse shape with 1 s of loading time and 1 s of rest time. The test duration was 3,600 cycles and the test temperature was 40 °C for uniaxial and 50 °C for triaxial loading. The

maximum axial stress for uniaxial loading was 100 kPa. The maximum axial stress for triaxial loading was 200 kPa and 100 kPa confining pressure. Figs. 3 and 4 show the uniaxial and triaxial test results.

In order to reduce the number of tests, the following tests will be performed for the combinations with unmodified binder BND 60/90 and PMB 45/80-55. The combinations with PMB 45/80-55 binder showed a little higher resistance to deformations. In the following stages of the research the rutting resistance and fatigue performance will be evaluated for other combinations as well.

4.2 Wheel Tracking Test

To perform rut resistance test, a wheel tracking apparatus is used to simulate the effect of traffic and to measure the deformation susceptibility of asphalt concrete samples. Tests were performed according to standard LVS EN 12697-22 method B (wheel tracking test with small size device in air). This test method is designed to repeat the stress conditions observed in the field therefore can be categorized as simulative. The asphalt mixture resistance to permanent deformation is assessed by the depth of the track and its increments caused by repetitive cycles (26.5 cycles/min) under constant temperature (60 °C). The rut depths are monitored by means of two LVDTs (linear variable displacement transducers), which measure the vertical displacements of each of the two wheel axles

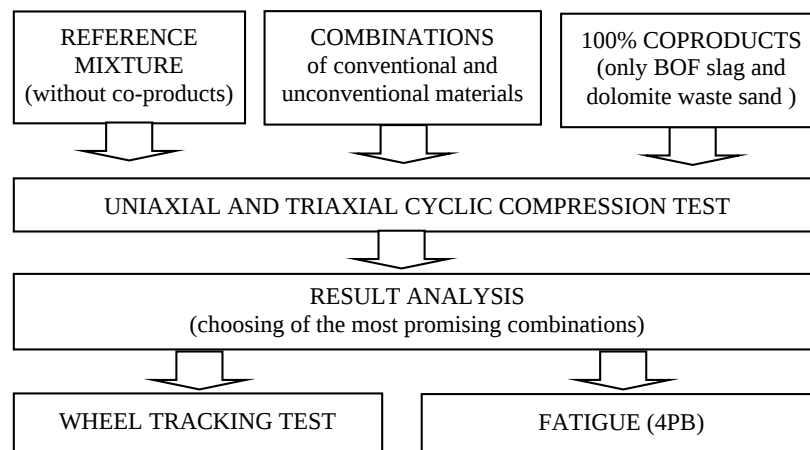


Fig. 2 Performance evaluation plan.

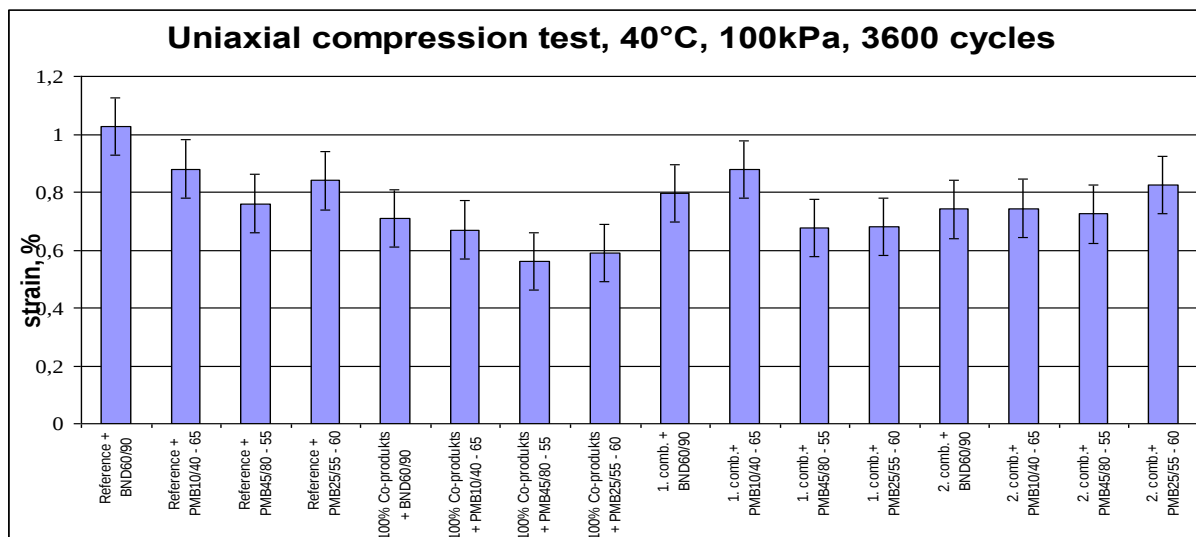


Fig. 3 Uniaxial compression test results.

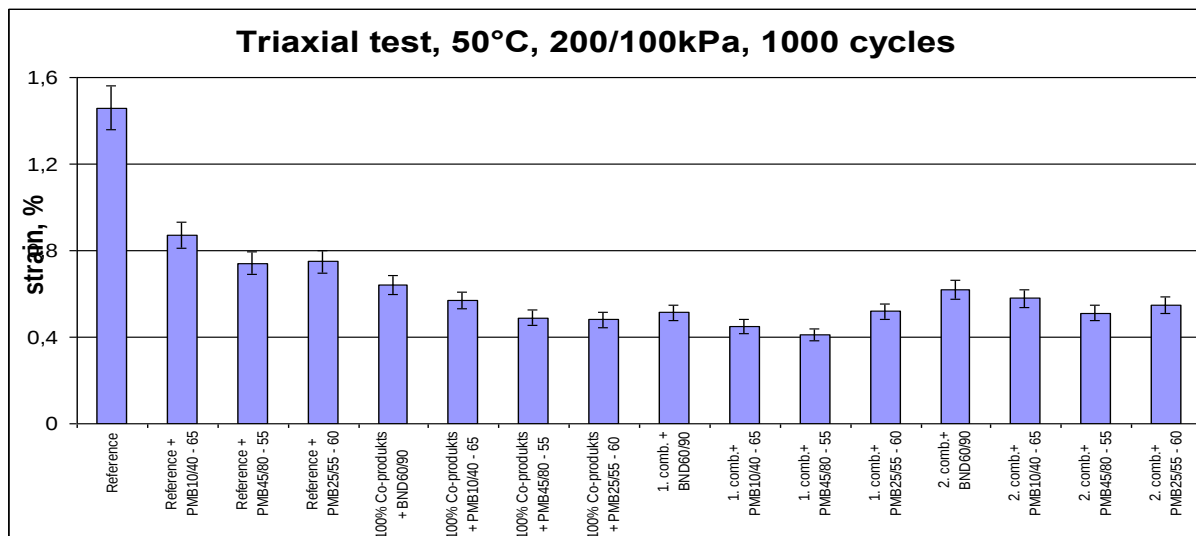


Fig. 4 Triaxial test results.

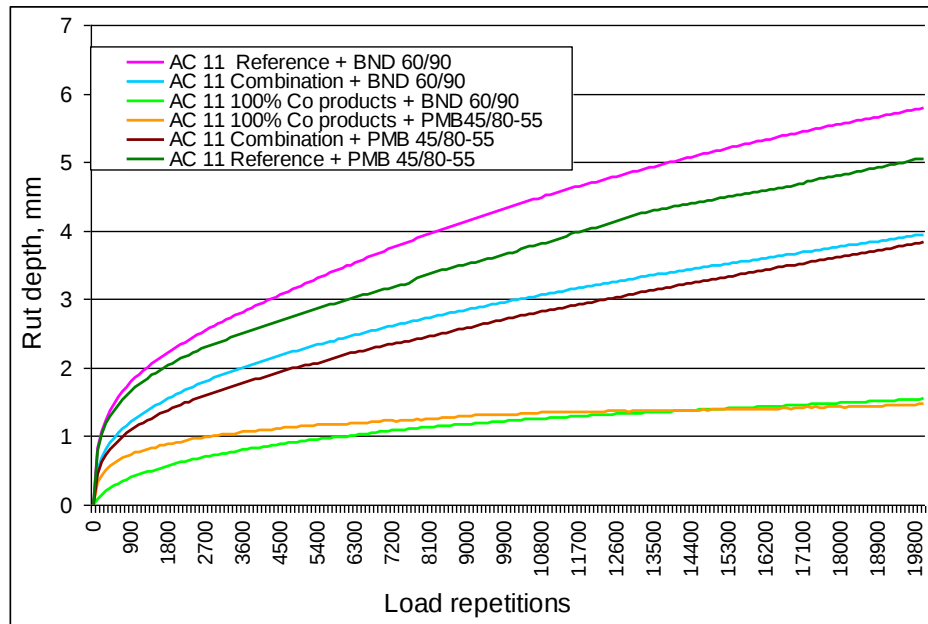


Fig. 5 Wheel tracking test results.

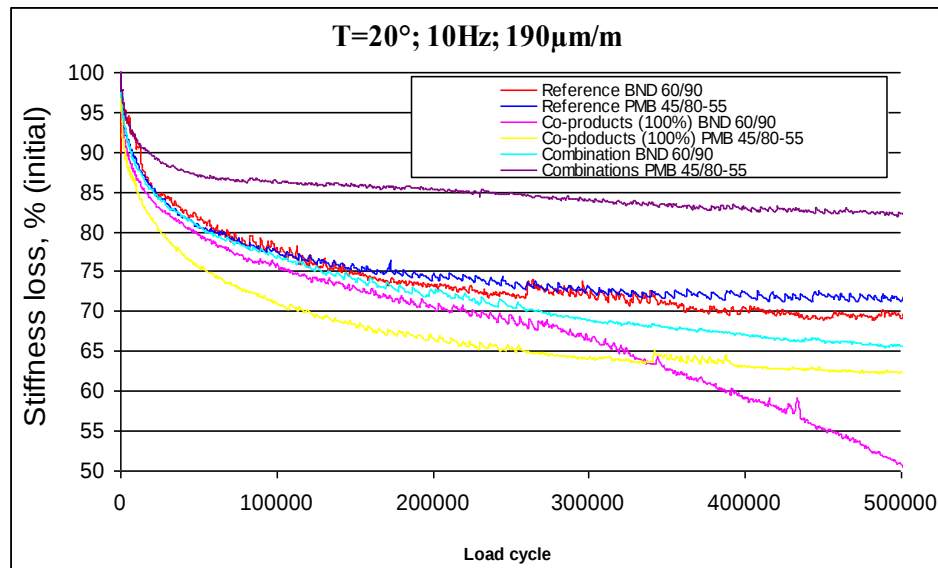


Fig. 6 Fatigue test results: stiffness reduction curves.

independently as rutting progresses. Fig. 5 provides a summary of rut resistance properties of the test specimens.

The obtained results demonstrate that the largest rut depth appears for the reference mixture with unmodified bitumen. The results for reference mixture with SBS modified bitumen are only slightly better. The asphalt concrete mixture which was produced entirely from co-products shows high resistance to

permanent deformations, having an average rut depth value of 1.54 mm and wheel tracking slope of 0.12 mm/1,000 cycles. The mixture with combination of co-product and conventional aggregate had somewhat worse test results.

4.3 Fatigue

To determine the fatigue life of the prepared asphalt concrete mixes, a four-point bending fatigue test was

conducted. The test was run at 20 °C, 30 Hz (according to LVS EN 12697-24) at 190 $\mu\text{m/m}$ strain level. The beams were compacted in the laboratory by using roller compactor. They were saw cut to the required dimensions of 50 mm wide, 50 mm high and 400 mm long. The failure criterion used in the study is the traditional 50% reduction in initial stiffness. The stiffness reduction curves are shown in Fig. 6. The obtained results indicate that mixture with BOF steel slag and dolomite sand waste (100% co-product) showed less resistance to fatigue, compared to results for mixture made with conventional aggregates and combined mixture. The mix designs that include exclusively dolomite aggregates as well as the combination of dolomite and slag in coarse portion plus waste sand in fine aggregate portion exhibit slightly higher fatigue life compared to other combinations. The fatigue life exceeded 500 thousand cycles for all the combinations with the exception of 100 percent by-product mixtures made with BND 60/90 bitumen. However, to verify the findings more extensive laboratory research is needed—this will allow determining the relationship between tensile strain at the bottom of the beam and the number of load applications before cracking.

5. Conclusions

Physical and mechanical properties of steel slag aggregates and dolomite sand waste are comparable with the characteristics of conventional natural aggregate usually used in transportation infrastructure.

The results of wheel tracking test and cyclic compression show that mixtures with high deformation resistance were prepared in laboratory using two types of co-products.

The analysis of fatigue resistance results shows that the mixtures made with steel slag and local limestone in coarse portion plus dolomite sand waste in sand and filler portions exhibit slightly higher fatigue resistance than the conventional mixtures. However, mixtures from 100% steel slag and dolomite waste sand show

less resistance to fatigue. To verify the findings more extensive laboratory research is needed—this will allow determining the relationship between tensile strain at the bottom of the beam and the number of load applications before cracking.

Acknowledgement

This work has been supported by the ERDF (European Regional Development Fund) activity No.2.1.1.1. “Atbalsts zinātnei un pētniecībai” (support for the science and research) within the project: No.2010/0254/2DP/2.1.1.1.0/10/APIA/VIAA/015.

References

- [1] Huang, Y. H. 1993. *Pavement Analysis and Design*. New Jersey: Prentice-Hall, Inc. ISBN: 0-13-655275-7.
- [2] Mallick, R. B., and El-Korchi, T. 2009. *Pavement Engineering: Principle and Practice*. London: CRS Press, Taylor and Francis Group. ISBN: 978-1-4200-6029-4.
- [3] Skinskas, S., Gasiūniene, V. E., Laurinavičius, A., and Podagėlis, I. 2010. “Lithuanian Mineral Resources, Their Reserves and Possibilities for Their Usage in Road Building.” *The Baltic Journal of Road and Bridge Engineering* 5 (4): 218-28. ISSN: 1822-4288, 2010.
- [4] Yilmaz and Sutas, 2012. Electric-ARC Furnace Slag Utilization in Hot Mix Asphalt. Proceedings of the 5th Eurasphalt & Eurobitume Congress, Istanbul, Turkey.
- [5] Kandhal and Hoffman, 1997. Evaluation of Steel Slag Fine Aggregate in Hot Mix Asphalt Mixtures, Trans. Res. Rec.: Journal of the Transportation Research Board, Vol. 1583 pp 28-36, USA.
- [6] The European Slag Association: “EUROSLAG”. 2006. *Legal Status of Slags*. Position paper. Accessed August 10, 2011. <http://www.euroslag.com>.
- [7] Gintalas, V. 2010. “Possibilities for the Improvement of the Quality of Design Solutions in the Gravel Road Reconstruction Projects.” *The Baltic Journal of Road and Bridge Engineering* 5 (3): 177-84. ISSN: 1822-4288.
- [8] Xirouchakis, D., and Manolakou, V. 2011. “Properties of EAF Slag Produced in Greece: A Constructional Material for Sustainable Growth.” In *Proceedings of 5th International Conference Bituminous Mixtures and Pavements*, June 1-3, 2011, Thessaloniki, Greece, pp. 287-97.
- [9] Pasetto, M., and Baldo, N. 2011. “Mix Design and Performance Characterization of Bituminous Mixtures with Electric Arc Furnace Steel Slags.” In *Proceedings of 5th International Conference Bituminous Mixtures and*

- Pavements*, June 1-3, 2011, Thessaloniki, Greece, pp. 748-57, 287-97.
- [10] Haryanto, I., and Takahashi, O. 2007. "Effect of Aggregate Gradation on Workability of Hot Mix Asphalt Mixtures." *The Baltic Journal of Road and Bridge Engineering* 2 (1): 21-8. ISSN: 1822-4288.
- [11] Bagampadde, U., Al-Abdul Wahhab, H. I., and Aiban, S. A. 1999. "Optimization of Steel Slag Aggregates for Bituminous Mixes in Saudi Arabia." *Journal of Materials in Civil Engineering* 11 (1): 30-5. ISSN: 0899-1561.
- [12] Korjakins, A., Gaidukova, S., Šahmenko, G., Bajāre, D., and Pizele, D. 2008. "Investigation of Alternative Dolomite Properties and Their Application in Concrete Production." *Construction Science* 9: 64-71. ISSN: 1407-7329.
- [13] Roberts, F., Mohammad, L., and Wang, L. 2002. "History of Hot Mix Asphalt Mixture Design in the United States." *Journal of Materials in Civil Engineering* 14 (4): 279-93.
- [14] Sivilevičius, H., Podvezko, V., and Vakriniene, S. 2011. "The Use of Constrained and Unconstrained Optimization Models in Gradation Design of Hot Mix Asphalt Mixture." *Construction and Building Materials* 25 (1): 115-22.
- [15] Sivilevičius, H., and Vislavičius, K. 2008. "Stochastic Simulation of the Influence of Variation of Mineral Material Grading and Dose Weight on Homogeneity of Hot Mix Asphalt." *Construction and Building Materials* 22 (9): 2007-14.